

COOLSPAN® TECA

Thermally and Electrically Conductive Adhesive

COOLSPAN® Thermally & Electrically Conductive Adhesive (TECA) film is a thermosetting, epoxy based, silver filled adhesive film used to bond circuit boards to heavy clad metal backplanes, heat sink coins and RF module housings. The adhesive can be used as an alternative to fusion bonding, sweat soldering, mechanical, or press fit metal attachment. COOLSPAN TECA provides both a thermal and electrical conductive bond interface.

COOLSPAN TECA film is supplied in sheet form on a PET carrier and is easy to handle when converting into preforms and when peeling from the carrier. Common converting processes include laser, steel rule die (SRD), router, and water jet cutting.

COOLSPAN TECA film has outstanding chemical resistance, and high temperature performance and will survive lead-free solder processing.

Processing Guidelines: The following processing guidelines provide a framework for working to identify the best set of parameters for a given application. Processing conditions may vary based on application and curing processes.

Adhesive and Surface Preparation: Allow adhesive to reach room temperature while strictly avoiding moisture condensation. Clean metal surfaces free of oils or other contaminants will provide for the best adhesion results. Cleaning with a solvent such as a reagent grade isopropyl alcohol is recommended.


Pre Tack Conditions: 125C for 5 minutes at 50 psi.

Cure Temperature and Time: 175C for 45 minutes, or 150C for 60 minutes. Temperature measured at adhesive.

Cure Pressure: Cure pressure will be dependent on factors such as size, flatness, and surface roughness. As such, it is recommended that a DOE (design of experiment) be used to identify a range of pressure that will ensure adequate wetting to both surfaces. A range of 80 psi to 140 psi serves as good range of pressures for such a DOE.



Data Sheet

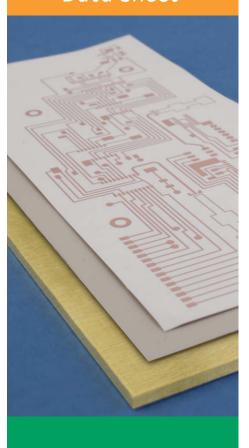

FEATURES:

- Thermally and Electrically Conductive Bond Interface
- Supplied on PET carrier
- Easily converted to pre-forms and easily handled
- Low flow during pressure cure
- High bond strength
- Thermally robust
- Chemically resistant
- Lead-free solder compatible

TYPICAL APPLICATIONS:

- Alternative to heavy clad laminates
- Post fabrication metal backplane attachment
- Power amplifier heat sink coin attachment
- RF circuit board module assembly



Film (Uncured) Typical Properties

| Property | Typical Value [1] | Units | Condition/Test Method |
|-------------------|--------------------------------|-----------------|------------------------------|
| Material Type | silver filled epoxy film | _ | _ |
| Thickness | 0.002± 0.0005 0.004± 0.0005 | inch | micrometer |
| Shelf Life [2] | 3 minimum | months from DOS | IPC 4101C, 3.17, Condition 2 |
| Work Life | 3 | months | <23C & <50% RH |
| Storage Life | 12 | months from DOM | 5C (41F) |
| DSC Peak Exotherm | 198 | С | DSC |
| Tensile Strength | 705 | psi | IPC-TM-650 2.4.19 |
| Mandrel Test | <0.125 | inch | ASTM D4338 |

Cured Material Typical Properties

| Property | / | Typical Value [1] | Units | Condition/Test Method |
|------------------------|-------------|-------------------|--------|--|
| CTE below Tg | | 45 | ppm/°C | TMA IPC-TM-650, 2.4.24.5 (modified) |
| CTE above Tg | | 70 | ppm/°C | TMA IPC-TM-650, 2.4.24.5 (modified) |
| Tg | | 79 | С | DMA ASTM D5026 |
| Td | | 415 | С | ASTM D3850, TGA |
| Storage Modulus @ | -40C | 11,417 | | |
| | 0C | 7,446 | | |
| | 25C | 5,387 | MPa | DMA ASTM D5026 |
| | 100C | 751 | | |
| | 150C | 445 | | |
| Lap Sheer Strength, EN | IIG to ENIG | 2,000 | psi | ASTM D1002-05 |
| рН | | 6.2 | _ | 25C |
| Ionics | Chloride | 5.9 | | |
| | Sodium | <4 | ppm | MIL STD 883 Method 5011 |
| | Potassium | <35 | | |
| Ash Percent | | 85 | % | TGA |
| Volume, Resistivity | | 0.00038 | Ohm-cm | Four Point Probe, Laminated Plies |
| Thermal Conductivity | | 6.0 | W/m°C | Laser Flash, Free Film, Z-Axis |
| Solder Float | | Pass | | IPC-TM-650, 2.4.13 method B |

^[1] Typical values should not be used for specification limits, except where noted.

Ordering Information

Please contact Rogers Customer Service for pricing and availability. Please order using the following descriptions.

| Description | Thickness (inch) | Sheet Size, W x L (inch) |
|--------------------------------|------------------|--------------------------|
| COOLSPAN TECA 10X12 0020+-0005 | 0.002+/-0.0005 | 10 x 12 |
| COOLSPAN TECA 10X12 0040+-0005 | 0.004+/-0.0005 | 10 x 12 |

The information in this data sheet is intended to assist you in designing with Rogers' circuit materials. It is not intended to and does not create any warranties express or implied, including any warranty of merchantability or fitness for a particular purpose or that the results shown on this data sheet will be achieved by a user for a particular purpose. The user should determine the suitability of Rogers' circuit materials for each application.

These commodities, technology and software are exported from the United States in accordance with the Export Administration regulations. Diversion contrary to U.S. law prohibited.

COOLSPAN, Helping power, protect connect our world and the Rogers' logo are trademarks of Rogers Corporation or one of its subsidiaries. © 2017 Rogers Corporation, Printed in U.S.A., All rights reserved. Revised 1276 041717 Publication # 92-169

^[2] Guaranteed at least 3 months of shelf life remaining from date of shipment (DOS)